


粒度分布測定結果
(レーザー回折散乱式測定)

試料名	マイカ100MESH	D10	10.914 μm
グレード	建材向け	D50	42.743 μm
		D90	153.15 μm

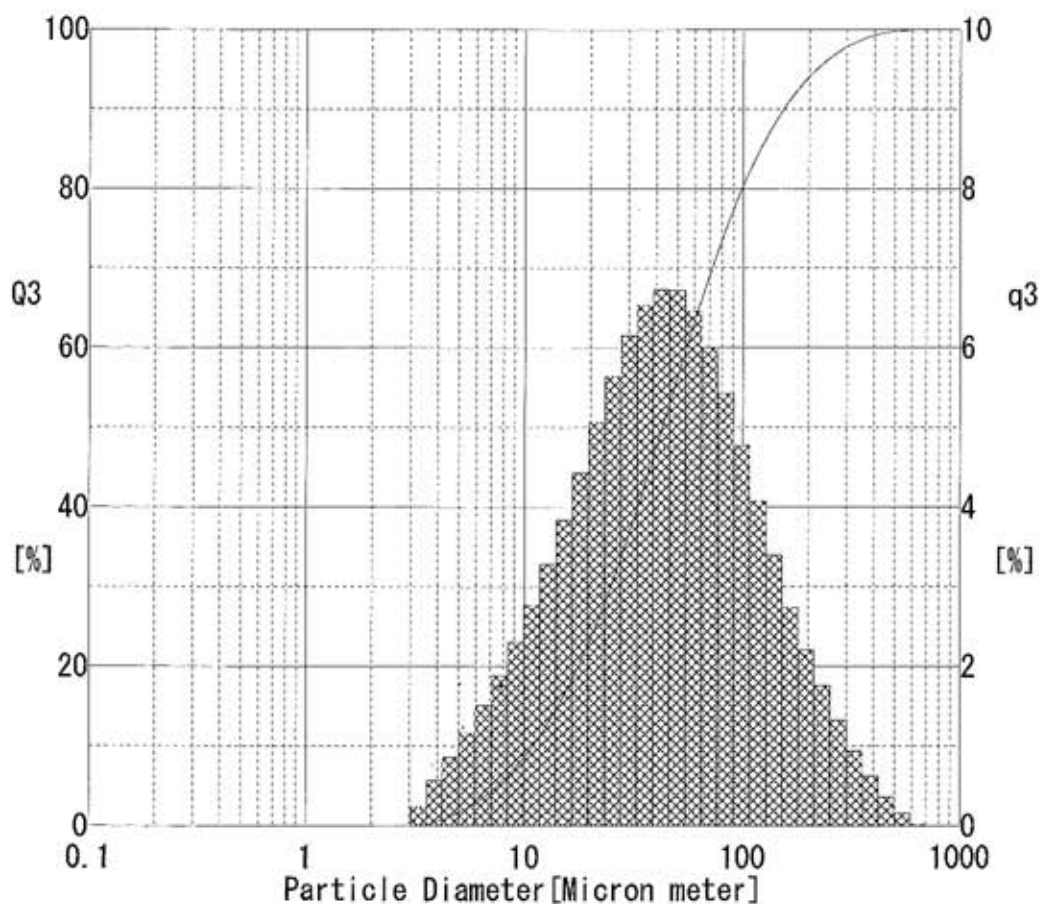

Ch.	粒径 μm	累積%	区間%	Ch.	粒径 μm	累積%	区間%	Ch.	粒径 μm	累積%	区間%
1	0.10	0.00	0.00	21	3.02	0.00	0.00	41	91.09	77.60	5.43
2	0.12	0.00	0.00	22	3.58	0.24	0.24	42	108.01	82.37	4.77
3	0.14	0.00	0.00	23	4.24	0.81	0.57	43	128.07	86.45	4.08
4	0.17	0.00	0.00	24	5.03	1.67	0.86	44	151.86	89.85	3.40
5	0.20	0.00	0.00	25	5.97	2.84	1.17	45	180.07	92.59	2.74
6	0.23	0.00	0.00	26	7.07	4.35	1.51	46	213.51	94.80	2.21
7	0.28	0.00	0.00	27	8.39	6.24	1.89	47	253.17	96.56	1.76
8	0.33	0.00	0.00	28	9.95	8.55	2.31	48	300.19	97.89	1.33
9	0.39	0.00	0.00	29	11.79	11.32	2.77	49	355.95	98.83	0.94
10	0.46	0.00	0.00	30	13.98	14.60	3.28	50	422.06	99.46	0.63
11	0.55	0.00	0.00	31	16.58	18.44	3.84	51	500.45	99.82	0.36
12	0.65	0.00	0.00	32	19.66	22.87	4.43	52	593.40	99.98	0.16
13	0.77	0.00	0.00	33	23.31	27.93	5.06	53	703.61	100.00	0.02
14	0.92	0.00	0.00	34	27.64	33.57	5.64	54	834.27	100.00	0.00
15	1.09	0.00	0.00	35	32.78	39.72	6.15	55	1000.00	100.00	0.00
16	1.29	0.00	0.00	36	38.86	46.25	6.53				
17	1.53	0.00	0.00	37	46.08	52.98	6.73				
18	1.81	0.00	0.00	38	54.64	59.70	6.72				
19	2.15	0.00	0.00	39	64.79	66.16	6.46				
20	2.55	0.00	0.00	40	76.82	72.17	6.01				